



Crosslinked Pyrazole Functionalized Resin Complexes of Transition Metals as Polymeric Catalysts for Hydrogen Peroxide Decomposition

G. RATHIKA NATH¹ and K. RAJESH²

¹Department of Chemistry, Sree Ayyappa College for Women, Chunkankadai, Nagercoil, Tamilnadu (India).

²Department of Chemistry, University College, Trivandrum, Kerala - 695 034 (India).

*Corresponding author: E-mail: rajesh_k_k@yahoo.com

(Received: June 10, 2011; Accepted: July 20, 2011)

ABSTRACT

Functionalized polymers are found to be highly efficient in immobilizing transition metal ions. The activity of Fe(III), Co(II), Ni(II) and Cu(II) complexes of polystyrene bound pyrazole resin have been tested towards the decomposition of hydrogen peroxide. The reactions show a first order dependence on the concentration of both the substrates and the catalyst. The metal complexes having less cross linking at the backbone and ring-activating group near the active site show high catalytic efficiency.

Key words: Metal complexes, Polymer supported ligands, poly-styrene supported ligands, Pyrazole ligands, Hydrogen peroxide.

INTRODUCTION

The use of polymer catalysts has become a powerful methodology in modern synthetic organic chemistry. Within the area of functionalized cross-linked polymers acting as catalysts, the polymer matrices can play

- i) A role of mere support for catalytic sites thus facilitating the work-up of the reaction products
- ii) A direct control of the reaction kinetics which depends on the loading and distribution of catalytic sites along the polymer backbone

Easy recovery and reuse, simplified reaction work-up and potential to conduct in a flow reactor or flow membrane reactor for continuous production are among the attractive features of using macromolecular chiral catalysts^{1,2}.

The technical development of majority of the polymer supported metal complex catalysts based on macroporous polystyrene-based resin has been limited due to two main reasons^{3,4}. The first one is the catalyst instability arising from the leaching of metal complex from the support. The second arises from an inherent belief that the normal


polymer supports would be too thermooxidatively unstable to be used in anything other than mild oxidation processes. An upper operating temperature limit of ~200°C is usually envisaged. From thermogravimetric studies, pyrazole polymers are identified as a potentially important and versatile polymer support due to its exceptional thermal stability.

The catalytic properties of metal complexes derived from pyrazole containing ligands have been studied⁵.

Decomposition of hydrogen peroxide:

The decomposition of hydrogen peroxide is often employed as a standard reaction to determine the catalytic activity of a metal complex⁶⁻⁹.

Metal ions as such or their complexes have been shown to possess enzyme like activity. The metal ion catalyzed disproportionation of H₂O₂ has received much attention which is mainly stimulated by the natural occurrence of a heme-iron enzyme called catalase which enhances the decomposition dramatically¹⁰.



The reaction is also catalyzed by Cu (II) complexes¹¹⁻¹³ provided the coordination sphere is accessible for H₂O₂ and HOO⁻.

The peroxides are cheap and readily available on a large scale from auto-oxidation of tertiary hydrocarbons. There has been and continues to be a lot of activity directed towards developing potentially selective catalysts for the decomposition of peroxides.

The decomposition reaction usually obeys first order kinetics and the study is important in understanding oxygen transport in polymer metal chelates.

EXPERIMENTAL

Preparation of the polymer bound pyrazole metal complexes

The synthesis of the polystyrene bound pyrazole complexes involves the reported method¹⁴

Reagents and Materials

All reagents used were of AnalaR grade. H₂O₂ (40 % v/v) was used as such from NICE chemicals.

Decomposition of hydrogen peroxide

Polymer supported pyrazole linked metal complex (100 mg) was shaken with hydrogen peroxide solution (0.4 V, 100 ml). Taking aliquot amounts and titrating against standard KMnO₄ (0.02N) determined the amount of H₂O₂ remaining after definite period of time. The course of decomposition was followed over a period of 3 hours. A blank experiment was also conducted. Similar experiments were carried out by varying the conditions such as temperature, amount of catalyst and the concentration of H₂O₂. Effects of the macromolecular factors like the degree of cross-linking and structural environment on the decomposition reaction were also studied by carrying out similar experiments.

RESULTS AND DISCUSSION

The catalytic activity of the pyrazole bound metal chelates were determined on the decomposition of H₂O₂ in aqueous medium.

Definite amount of metal complex was shaken with H₂O₂ of known volume and strength. The amount of H₂O₂ decomposed was followed by withdrawing a known amount of H₂O₂ at definite intervals of time and titrating it against standard KMnO₄.

The rate constant K of the decomposition pattern of H₂O₂ using different polymeric catalysts, calculated using the first order equation

$$K = \frac{2.308}{t} \log \frac{a}{(a-x)}$$

where a is the initial concentration of the reactant and x is the amount reacted in time t, are given in table 1.

The activation energies of catalyzed and uncatalyzed reactions were compared to get an idea

of their relative efficiencies. The activation energies were calculated using the Arrhenius equation,

$$\log \frac{k_2}{k_1} = \frac{E_a}{2.303R} \left(\frac{1}{T_1} - \frac{1}{T_2} \right)$$

All the complexes, except that of Co (II) were found to increase the rate of decomposition, proving their catalytic activity. The poor activity of Co (II) complexes of the ligand can be attributed to its assigned geometry, which do not favour decomposition reaction. Among the four metal complexes, Cu (II) complexes show the highest catalytic activity.

Table 2: Influence of H₂O₂ concentration on the rate of decomposition

[H ₂ O ₂]	Rate constant K (s ⁻¹)	
	Pyrazole	No catalyst
0.4 V	6.24 × 10 ⁻³	9.52 × 10 ⁻³
0.6 V	6.73 × 10 ⁻³	1.04 × 10 ⁻²
0.8V	7.31 × 10 ⁻³	1.54 × 10 ⁻²

Conditions

R = OCH₃, 2% DVB cross-linked resin =100 mg, [H₂O₂] = 0.4 V, Temperature = 303 K, Time = 3 h

Table 4: Influence of degree of cross-linking of complexes on the rate of decomposition

% of cross linking	Rate constant K (s ⁻¹) Pyrazole complex	
	Fe (III)	Cu (II)
2	6.24 × 10 ⁻³	9.55 × 10 ⁻³
5	3.45 × 10 ⁻³	7.21 × 10 ⁻³
10	2.87 × 10 ⁻³	3.25 × 10 ⁻³
15	2.40 × 10 ⁻⁴	5.10 × 10 ⁻⁴
20	1.85 × 10 ⁻⁴	4.32 × 10 ⁻⁴

Conditions

R = OCH₃, 2% DVB cross-linked resin =100 mg, [H₂O₂] = 0.4 V, Temperature = 303 K, Time = 3 h

Table 1: Effect of polymer metal complexes on the rate of H₂O₂ decomposition

Metal ion	Rate constant K (s ⁻¹)	
	Pyrazole	No catalyst
Fe (III)	6.24×10 ⁻³	
Co (II)	5.21×10 ⁻⁴	3.29×10 ⁻⁴
Ni (II)	5.33×10 ⁻³	
Cu (II)	9.55×10 ⁻³	

Conditions

R = OCH₃, 2% DVB cross-linked resin =100 mg, [H₂O₂] = 0.4 V, Temperature = 303 K, Time = 3 h

Table 3: Influence of amount of catalyst on the rate of decomposition of H₂O₂

Amount of catalyst (mg)	Rate constant K (s ⁻¹) Pyrazole complex	
	Fe (III)	Cu (II)
50	5.78 × 10 ⁻³	8.94 × 10 ⁻³
100	6.24 × 10 ⁻³	9.55 × 10 ⁻³
150	7.18 × 10 ⁻³	1.27 × 10 ⁻²
200	8.23 × 10 ⁻³	2.12 × 10 ⁻²

Conditions

R = OCH₃, 2% DVB cross-linked resin =100 mg, [H₂O₂] = 0.4 V, Temperature = 303 K, Time = 3 h

Table 5: Influence of degree of cross-linking of complexes on the rate of decomposition

% of cross linking	Rate constant K (s ⁻¹) Pyrazole complex	
	Fe (III)	Cu (II)
H	1.92 × 10 ⁻³	3.25 × 10 ⁻³
Me	3.12 × 10 ⁻³	6.25 × 10 ⁻³
OMe	6.24 × 10 ⁻³	9.55 × 10 ⁻³
Cl	4.8 × 10 ⁻⁴	5.73 × 10 ⁻⁴
NO ₂	2.75 × 10 ⁻⁴	3.30 × 10 ⁻⁴

Conditions

R = OCH₃, 2% DVB cross-linked resin =100 mg, [H₂O₂] = 0.4 V, Temperature = 303 K, Time = 3 h

Effect of various factors on decomposition:

In order to establish the relation between rate of decomposition and various factors such as substrate concentration, amount of catalyst, temperature, degree of cross-linking and structural environment of the ligand, studies on aqueous hydrogen peroxide solutions at varying conditions were carried out.

Influence of substrate concentration

The decomposition patterns of aqueous H_2O_2 solutions of varying concentrations were studied in presence of a definite amount of catalyst and the rate constant for each case are given in table 2.

The rate of the decomposition reaction was found to be increasing with increase in substrate concentration.

Effect of amount of catalyst

The decomposition patterns of aqueous H_2O_2 solutions of definite volume and concentration were studied in presence of varying amount of catalysts after thermostating at 293 K and the rate constant for each case are given in table 3.

The results obtained prove the linear relationship between rate constant and the amount of catalyst.

Influence of degree of cross-linking of polymer backbone

The study of the effect of degree of cross-

linking of the polymer supported metal complexes on the decomposition pattern has been studied and the results are tabulated in table 4. A gradual decrease in catalytic efficiency with increase in the degree of cross-linking was noticed. With increasing degree of cross-linking, the hydrophobicity of the polymer increases which in turn decreases the accessibility of reactive groups. Thus the reactive sites in highly cross-linked systems will not be readily available to the low molecular weight species.

Influence of structural environment of the ligand

Polymer supported pyrazole complexes with different substituents groups such as phenyl, 4'-methoxy phenyl, 4'-methyl phenyl, 4'-chloro phenyl and 4'-nitro phenyl were used as catalysts and the rate of decomposition was estimated for each case after a fixed time. The results are tabulated in table 5.

Complexation studies revealed that the methoxy substituted complex possess higher metal intake than others. The same trend was noticed for their activity on the decomposition reaction. The inductive and the mesomeric effect of the substituents groups influence the electron delocalisation over the chelating ligand. The electron availability of the coordinating sites, in turn, determines the basicity of the ligand function. Methoxy and methyl groups, being electron donors, increases the basicity which promotes the electron transfer process between the metal complex and the substrate. On the other hand, the chloro and nitro groups decrease the basicity of the functional

Table 6: Influence of temperature on the rate of decomposition of pyrazole complexes

Catalyst	Metal ion	K_{30}	K_{40}	K_{50}	E_a
DVB cross linked pyrazole complex	Fe (III)	6.21×10^{-3}	8.23×10^{-3}	1.11×10^{-2}	23.67
	Co (II)	4.50×10^{-3}	5.16×10^{-3}	7.41×10^{-3}	20.60
	Ni (II)	5.31×10^{-3}	7.45×10^{-3}	1.02×10^{-2}	26.5
	Cu (II)	9.52×10^{-3}	1.15×10^{-2}	1.39×10^{-2}	15.18
EGDMA cross linked pyrazole complex	Fe (III)	9.2×10^{-3}	1.19×10^{-2}	1.52×10^{-2}	20.42
	Co (II)	6.1×10^{-3}	9.84×10^{-3}	1.13×10^{-2}	24.65
	Ni (II)	7.77×10^{-3}	1.03×10^{-2}	1.34×10^{-2}	22.16
	Cu (II)	1.1×10^{-2}	1.28×10^{-2}	1.49×10^{-2}	11.98
No catalyst		3.29×10^{-4}	7.8×10^{-4}	1.52×10^{-3}	62.06

Conditions: $[H_2O_2] = 0.4$ V, 2 % cross-linked resin = 100 mg, Time = 3 h

groups due to their electron withdrawing nature.

Influence of temperature

The variation in the rate of decomposition of aqueous H_2O_2 solutions of definite volume and concentration thermostated at different temperatures were studied with definite amount of catalysts. The rate constant values when temperature is varied from 20°C to 60°C are given in table 6.

From the results it is clear that the rate constants bear a linear relationship with temperature. From kinetic studies, it is clear that the reaction follows first order kinetics. The activation energies of complex catalyzed decomposition were found to be much less than the uncatalyzed reaction, proving the high efficiency of catalysts on increasing the rate of the reaction.


DISCUSSION

Like metalloporphyrins in a living body, metal ions and their complexes can bind molecular oxygen rapidly and reversibly. Polymer metal complexes show specific behaviour in the binding of small molecules since the polymer backbone affects the reaction to a large extent.

The action of complex carriers in the reaction is the picking up of oxygen from one end and diffusing inside as the oxygenated complex and finally transferring oxygen to the other side. The decomposition reaction is accompanied by the liberation of molecular oxygen, with the reduction of metal ions in the complex to a lower oxidation state resulting in the shrinking of the polymer. This observation is dependant on the geometry of the polymer structure.



A transient complex with a new geometry which is capable of accepting an electron is formed due to the stretching of the metal-ligand bond, which causes lowering of the activating energy and enhancement of catalytic activity. The energy required to rearrange the complex structure is the activation energy of the electron transfer¹⁵. The decomposition could thus be explained by the following scheme

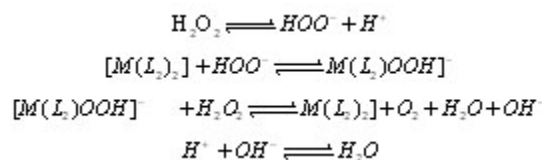

CONCLUSION

From the studies it was found that Fe(III), Co(II), Ni(II) and Cu(II) complexes of polystyrene bound pyrazole resin have marked activity towards the decomposition of hydrogen peroxide. The reactions show a first order dependence on the concentration of both the substrates and the catalyst. The metal complexes having less cross linking at the backbone and ring-activating group near the active site showed high catalytic efficiency. This is only a preliminary study which shows that crosslinked polymeric pyrazole functionalized metal complexes have marked activity towards Hydrogen peroxide decomposition. The main utility of this knowledge is that the pyrazole functionalized resin complexes with various metals can be used to catalyse many organic reactions in which nascent oxygen is utilized. Further studies in such reactions like utility for epoxidation etc are planned.

ACKNOWLEDGEMENTS

The authors wish to acknowledge funding by the UGC under the Minor Project schemes.

REFERENCES

1. Itsuno, Shinichi. *Polymeric Chiral Catalyst Design and Chiral Polymer Synthesis*. Wiley-VCH (2011)
2. Jacobsen, E.N., Pfaltz, A., Yamamoto, Y. *Comprehensive Asymmetric Synthesis*. Springer, (1999)
3. Tokoyama, K., Nishizawa, M., Kimura, T., Suzuki, T.M., *Bull. Chem. Soc. Jpn.* 58: 3271

- (1985)
4. Sherrington, D.C., Simpson, S. *J. Catal.* **131**: 115 (1991)
 5. Malachowski, M.R., Carden, J., Davidson, M.G., Driessen, W.L., Reedijk, J., *Inorg. Chim. Acta*, **257**: 59 (1997)
 6. Nina Kann. *Molecules* **15**: 6306-6331 (2010)
 7. Pepper, K.W., Paisley, H.M., Young, M.A. *J. Chem. Soc.* 4097 (1953).
 8. Sreekala, R., Yusuff, K.K.M. *Ind. J. Chem*, **34A**: 994 (1995).
 9. Joseph, D.L., Herve, G., *Environ. Sci. Technol.* **33**: 2726 (1999).
 10. Jones, P., Wilson, I., *Met. Ions Biol. Syst.* **7**: 185 (1978).
 11. Sigel, H., Wyss, K., Eischer, B.E., Prijs, B., *Inorg. Chem.*, **18**: 1354 (1979).
 12. Oishi, N., Takeuchi, M., Nishida, Y., Kida, S. *Polyhedron* **3**: 157 (1984).
 13. Nath, M., Kamaluddin, Cheema, J. *Ind. J. Chem.* **32A**: 108 (1993).
 14. G.Rathika Nath, T. Radhakrishnan. Synthesis and Reactivity in Inorganic, *Metal-Organic and Nano-Metal Chemistry* **35**: 491-498 (2005).
 15. Tsuchida, E., Nishide, H., Nishiyama, T. *Macromol. Chem.* **175**: 3047 (1974).